arXiv:0906.0944v4 [cond-mat.stat-mech] 20 Apr 2010

Quantum ferroelectrics near weak first order transition

Nabyendu Das[1] and Suresh G. Mishra[2*]
[1]*Institute of Physics, Bhubaneswar 751005, India*
[2]*National Institute of Science Education and Research, Bhubaneswar 751005, India.*

(Dated: April 21, 2010)

Considering a recent experimental indication that certain doped dielectric materials, such as $SrTiO_3$ and $KTaO_3$, are on the verge of a first order quantum phase transition, the effects of order parameter fluctuations in those materials near such a transition are discussed. We start with a semi-microscopic action, where transverse paraelectric(or optical mode) fluctuations are controlled by hydrostatic pressure via strain coupling, which above a certain value of strength, kills the second order transition. Using self-consistent parquet re-summations, which retain the leading fluctuation effects in four point vertex function, we write the free energy of the system. This fluctuation re-normalized free energy is then used to discuss the possibility of first order transition at zero temperature as well as at finite temperature. An asymptotic analysis of fluctuation corrected vertices, with strain induced long range interaction, predicts small but a finite jump in the order parameter near the mean field quantum critical point at zero temperature. In the case of finite temperature transition, near quantum critical point such a possibility is found to be extremely weak. The formalism is quite general and is applicable to certain class of systems undergoing weak quantum first order phase transition.

PACS numbers: 64.70. Tg, 63.70.+h, 77.80. Bh

I. INTRODUCTION

The static dielectric susceptibility in the materials like $SrTiO_3$ and $KTaO_3$ does not show any divergence down to 0K, it rather saturates at a very high value ($\mathcal{O}(10^4)$). Ferroelectric transitions in materials which are similar in structure, for example in $BaTiO_3$, are of displacive type and are well described by softening of a zone center transverse optical mode at some finite temperature. This scenario, that is, the absence of transition and the saturation at high dielectric susceptibility, has been attributed to the smallness of the zero temperature gap in the corresponding zone centered optical mode. Thus quantum fluctuations become relevant in these materials at low temperature. These materials are called quantum paraelectrics[1]. There is a revival of interest, particularly regarding a quantum phase transition, effects of the quantum critical point at finite temperature[2],[3] and the nature of phase transition in these materials[4]. The effects of pressure[5] and impurities on the dielectric susceptibilities have been well studied experimentally. A general consensus arising form these experiments is that the application of hydrostatic pressure moves the system away from criticality and the possibility of phase transition is suppressed. One needs to apply, what is termed as, *a negative pressure* to induce phase transitions in these materials. One way to simulate negative pressure is to put non-polar impurities which creates local pressure deficiencies. In this context, experimentally[7] one finds that $T_c \sim (n - n_c)^{\frac{1}{2}}$ (where n is the average impurity concentration and n_c is the critical value, typically 33%) which matches well with the theoretical estimated[2] transition temperature for pressure induced transition. In this case, the mean field $T_c \sim (p + p_c)^{\frac{1}{2}}$ (where p is hydrostatic pressure and p_c is the critical value). The exponent half is obtained when thermal fluctuations are treated at the Gaussian level. The similarity between effects of pressure and the impurity in the transition temperature can be attributed to the high density of impurity concentrations in these cases. Here the disorder effects seem to be small and a non-polar impurity essentially induces an internal pressure. One recent experimental report[6] indicates that these materials show phase separation near quantum critical point. This is clearly an indication of a weak first order transition. Unlike a strong first order transition, order parameter fluctuations are more important in materials undergoing very weak first order transition. One needs to study the effects of order-parameter fluctuations in four-point vertices in a proper self-consistent scheme. In this work, we use self-consistent parquet approximation to take proper account of the leading order fluctuation effects in a quantum paraelectric near such a weak first order transition. We consider a displacive type ferroelectric in its quantum limit. In these materials the atomic dipoles are believed to interact among themselves with a long range dipolar interaction and their collective excitations give rise to various optical modes. The long range nature of the dipolar interaction makes longitudinal optical modes rigid and therefore they do not contribute to the low temperature phenomena. On the other hand transverse modes do not gain extra rigidity, but acquire dipolar anisotropy. Thus we start with a model action with short range interaction without dipolar anisotropy and try to explore the results of order parameter fluctuations with an effective long range interactions among them, mediated by strain fluctuations. We also assume that the system has a strong crystal anisotropy, so that the two transverse directions do not mix up and the system splits up in two one component Ising type systems in two transverse directions. Since ferrolectric systems do possesses strong cubic anisotropy, such an assumption does not alter the basic nature of the transition mechanism in these systems. We therefore, use an effective Ising type model and look for the fluctuation effects in four point vertices. To retain the leading fluctuation effects in the vertex function along with their dependencies on the non-zero polarization, we calculate the free energy using a parquet diagrams. This fluctuation renormalized free energy indicates possibility of a first order transition at zero temperature and it also gives finite temperature corrections.

II. SUMMARY OF THE MEAN FIELD ANALYSIS

Considering the system to be at a constant pressure, we integrate out the strain fluctuations completely. Our starting effective action describes only polarization fluctuations with strain induced long range interactions among them and takes the following form.

$$\begin{aligned}\mathcal{A} &= \frac{1}{\beta}\sum_{q,n}\frac{1}{2}(\omega_n^2+r+cq^2)\phi_q\phi_{-q} \\ &+ \frac{u}{4!\beta}\sum_{q_1,q_2,q_3,n}\phi_{q_1}\phi_{q_2}\phi_{q_3}\phi_{-q_1-q_2-q_3} \\ &+ \frac{vL^{-d}}{4!\beta}\sum_{q_1,q_2,n}\phi_{q_1}\phi_{-q_1}\phi_{q_2}\phi_{-q_2}. \qquad (1)\end{aligned}$$

Here $\phi_q(\omega_n)$ describes the Fourier transform of local transverse polarization $\phi(x,\tau)$, q is the field momentum, $\omega_n = 2\pi n/\beta$ is the Matsubara frequency for Bosonic excitations, r and u are the quadratic and the anisotropic short range quartic coupling respectively and v is the isotropic long range part of the quartic coupling induced by strain and L^d is the system volume in d-spatial dimension. Hydrostatic pressure, as well as the non-polar impurity, couples to the optical mode via strain. It shifts the bare quadratic and quartic coupling r_0 to $r = r_0(1+p/p_0)$, where p_0 is a constant. Strain fluctuation induces a long range attractive interaction between the dipoles and is denoted by the effective quartic coupling v. $\phi_q(\omega)$ can be decomposed into two parts, P, the static(mean field) and $\psi(q,\omega)$, the fluctuating part as follows,

$$\phi_q = P\delta(q,\omega) + \psi(q,\omega). \qquad (2)$$

It is assumed that $<\psi(q,\omega)>=0$. In this approximation the action[1] can be written as

$$\begin{aligned}\mathcal{A} &= \frac{r}{2}P^2 + \frac{(u+v)}{4!}P^4 \\ &+ \frac{1}{2\beta}\sum_{n,q}(\omega_n^2+r+cq^2+(u/2+v/6)P^2)\psi_q\psi_{-q} \\ &+ P\frac{u}{3!\beta}\sum_{q_1,q_2}\psi_{q_1}\psi_{q_2}\psi_{-q_1-q_2} \\ &+ \frac{u}{4!}\sum_{q_1,q_2,q_3,n}\psi_{q_1}\psi_{q_2}\psi_{q_3}\psi_{-q_1-q_2-q_3} \\ &+ \frac{vL^{-d}}{4!\beta}\sum_{q_1,q_2,n}\psi_{q_1}\psi_{-q_1}\psi_{q_2}\psi_{-q_2} \qquad (3)\end{aligned}$$

The free energy is defined as the functional integral over $\mathcal{A}(\psi,P)$, i.e.

$$F = -\frac{1}{\beta}\log\left(\int \mathcal{D}\psi e^{-\beta H(\psi,P)}\right) \qquad (4)$$

The value of P is to be determined by minimizing the free energy F. Stability of a thermodynamic system requires the free energy to be positive. In a Landau theory, which neglects fluctuations completely, the the requirement becomes $(u+v)>0$. In that case the system should undergo a second order transition. On the other hand, for $(u+v)<0$, one needs higher order term with positive coefficient to ensure stability. In this case the system should undergo a first order transition. Though a strong first order transition is well described by mean field theory, a theory of weak first order transition in the limit $(u+v)\to 0^-$ needs proper account of the fluctuation effects.

III. FLUCTUATION CORRECTIONS TO THE FREE ENERGY AT ZERO TEMPERATURE

To describe the effects of the order parameter fluctuations near a weak first order phase transition, we need to calculate the fluctuation renormalized four point vertex functions. Here we propose a quantum generalization of the work done by Gadeker and Ramakrishnan[8,9] to calculate the renormalized four point vertices in *parquet approximation*. The technique involves summation of leading order diagrams at each order. It has also been shown to be equivalent to the renormalization group[10] calculation. It turns out that. at or near $d=4$ the diagrams which can be cut into two parts by cutting two lines in the same bubble, contribute to the leading order corrections. For example, the diagrams in figure [1] are important for the fluctuation corrections in short range vertices in parquet approximation. Since in this case the system acquires a small but non zero polarization P even above the mean field critical point, the polarization fluctuation becomes gaped, with the gap being proportional to P^2. Thus the free propagator for this system is given by,

$$G^{-1}(q,\omega_n) = r + cq^2 + \omega_n^2 + (u/2 + v/6)P^2 \qquad (5)$$

In the paraelectric phase $P = 0$. A bare theory predicts that at $T = 0$, the static dielectric susceptibility $\chi(0,0) \sim G(0,0) \sim 1/r$. Thus $r = 0$ is a point of instability in the paraelectric phase, and in a situation where there is no discontinuity in the order parameter at that point, it can be identified as a *quantum critical point*(QCP). In the vicinity of the critical point, correlation length becomes large, leading to dominance of the order parameter fluctuations. Moreover when $|u+v| \approx 0$, fluctuation corrections to the four point vertices become important. We will try to discuss the effects of fluctuations in the vicinity of the limit $|u+v| \to 0$, in developing non-zero spontaneous polarization near the transition point. Since in the case of a week first order transion, initially correlation length grows significantly, the bare vertices get strongly renormalized. Now using the propagator for the polarization fluctuation (eqn.[5]) we find the the leading order contribution from the first two diagrams of the figure[1] to the renormalization vertex function as follows,



FIG. 1: Parquet diagrams for the fluctuation corrections to the short interaction vertex u. It takes care of the loop corrections of the above type to all orders. Here each line corresponds to the propagator given by the equation[5].

$$\delta u = -u^2 \sum_n \int_0^\Lambda d^dq G^2(q,\omega_n) \qquad (6)$$

At $T = 0$, the frequency summation becomes an integral and the combination of the frequency sum and the d-dimensional integral can be replaced by a $d+1$-dimensional integral. Hence,

$$\begin{aligned} \delta u &\sim -u^2 \int_0^\Lambda d^{d+1}qG^2(q) \text{ which} \\ &\sim -u^2 K_4 \log \frac{\Lambda}{(r + (u/2+v/6)P^2)^{\frac{1}{2}}} \text{ in } 3D. \qquad (7) \end{aligned}$$

where K_d is a constant which is related to the surface area of a d-dimensional sphere of unit radius. It is given by,

$$K_d = (2^{d-1}\pi^{\frac{d}{2}}\Gamma(\frac{d}{2}))^{-1}. \qquad (8)$$

$K_d = \frac{1}{8\pi^2}$ and $\frac{1}{2\pi^2}$ in d=4 and d=3 respectively. The corrections to four point vertex δu has a logarithmic divergence as $r \to 0$ and $P \to 0$. We define the diverging logarithmic part as our parquet variable

$$x = \log \frac{\Lambda}{(r + (u/2+v/6)P^2)^{\frac{1}{2}}}. \qquad (9)$$

It is to be noted that the higher order diagrams will contribute a factor $(ux)^n$ compared to the lowest order contribution u^2x. Virtual processes which contribute factors like $u^m x^n$ $(m \neq n)$ compared to the lowest order, are neglected in the parquet approximation[11]. In this approximation, contributions from the third order term in the action(equation [3]) are negligible compared to the logarithmically diverging contributions coming from the fourth order terms. We define the renormalized proper four point vertices Γ_4 and Δ_4, with their bare values given as,

$$\Gamma_4^0 = u \text{ and } \Delta_4^0 = v. \qquad (10)$$

Summing over all the leading order corrections, we get the following equations in terms of the parquet variable x,

$$\begin{aligned} \frac{d\Gamma_4}{dx} &= -\frac{3}{2}K_{d+1}\Gamma_4^2(x) \\ \frac{d\Delta_4}{dx} &= -K_{d+1}\Gamma_4(x)\Delta_4(x) - \frac{1}{6}K_{d+1}\Delta_4^2(x) \qquad (11) \end{aligned}$$

The solutions of these equations can be written as,

$$\Gamma_4 = \frac{\Gamma_4^0}{1 + \frac{3}{2}K_{d+1}\Gamma_4^0 x}, \qquad (12)$$

It is to be noted that the parquet variable x contains Γ_4 and Δ_4. Thus the set of equations [12] defines coupled equations for Γ_4 and Δ_4. They need to be solved self-consistently to find out their dependencies on r and P. From Γ_4 and Δ_4 thus obtained, we can calculate the fluctuation renormalized free energy using the relation,

$$\frac{\partial^4 F}{\partial P^4} = \Gamma_4 + \Delta_4 \qquad (13)$$

We need to integrate (with proper boundary conditions) the above equation four times respect to P to get an expression for the free energy. Integrating the equation [13] once we get

$$\begin{aligned} \frac{\partial^3 F}{\partial P^3} &= \int_0^P (\Gamma_4 + \Delta_4)dP' = P(\Gamma_4 + \Delta_4) \\ &+ \int_0^P P' \frac{\partial}{\partial P'}(\Gamma_4 + \Delta_4)dP' + c(r) \qquad (14) \end{aligned}$$

Here $c(r)$ is a constant independent of P and equals to zero for the symmetry reason $(\partial^3 F/\partial P^3|_0 = 0)$. The second term in the right hand side of the above equation takes care of the P dependence of Γ_4 and Δ_4. To make our calculations simpler, we will neglect that term at this stage. Before doing so, we make an estimate of the corresponding error. The integral reads as,

$$\int_0^P \frac{2K_{d+1}(3\Gamma_4 + \Delta_4)^3 P'^2 dP'}{6r + [(3\Gamma_4 + \Delta_4) - \frac{K_{d+1}}{6}(3\Gamma_4 + \Delta_4)^2]P'^2} \qquad (15)$$

Since $K_{d+1} = \frac{1}{8\pi^2}$ in $d = 3$, $K_{d+1}(3\Gamma_4 + \Delta_4) \sim \mathcal{O}(10^{-2})$. Thus the contribution from the P-dependence of Γ_4 and

Δ_4 to the integral(15) becomes,

$$\begin{aligned}
&\frac{K_{d+1}}{3}(3\Gamma_4+\Delta_4)^3\int\frac{P'^2dP'}{6r+(3\Gamma_4+\Delta_4)P'^2}\\
\approx\ &\frac{K_{d+1}}{3}(3\Gamma_4+\Delta_4)^2P\approx 10^{-2}(3\Gamma_4+\Delta_4)P \qquad (16)
\end{aligned}$$

We see that, the P-dependence of Γ_4 and Δ_4 contributes two order of magnitude less compared to the other terms in the free energy. Thus we neglect the P dependence of Γ_4 and Δ_4 at this stage in calculating F. Integrating two more times, we get,

$$\frac{\partial F}{\partial P}=rP+\frac{1}{3!}(\Gamma_4+\Delta_4)P^3 \qquad (17)$$

At this stage to have a form of F suitable to describe the first order transition we need to retain the P dependence of Γ_4 and Δ_4.

$$\begin{aligned}
F &= \int_0^P(rP'+\frac{1}{3!}(\Gamma_4+\Delta_4)P'^3)dP'\\
&= \frac{1}{2}rP^2+\frac{(\Gamma_4(P)+\Delta_4(P))}{4!}P^4\\
&- \frac{1}{4!}\int_0^P P'^4\frac{d}{dP'}(\Gamma_4(p')+\Delta_4(P'))dP' \qquad (18)
\end{aligned}$$

To evaluate the above integral, we make the following substitution(using equation[9])

$$P^2=\frac{\Lambda e^{-x}-r}{(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6})} \qquad (19)$$

Contribution from the integral part in the previous equation is given by

$$\begin{aligned}
&- \frac{1}{4!}\int_{\log(\Lambda/r)}^{\log\frac{\Lambda}{r+(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6})P^2}}\left(\frac{\Lambda e^{-x}-r}{(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6})}\right)^2\\
&\times \frac{d}{dx}(\Gamma_4(x)+\Delta_4(x))dx\\
&= \frac{K_{d+1}}{4}\int_{\log(\Lambda/r)}^{\log\frac{\Lambda}{r+(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6})P^2}}(\Lambda^2e^{-2x}-2r\Lambda e^{-x}+r^2)dx\\
&= \frac{K_{d+1}}{4}(\frac{r}{2}(\Gamma_4+\Delta_4)P^2-\frac{1}{2}(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6})^2P^4\\
&+ r^2\log\frac{r}{r+(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6})P^2}). \qquad (20)
\end{aligned}$$

Thus we have the following expression for the free energy at zero temperature

$$\begin{aligned}
F &= \frac{K_{d+1}}{4}r^2\log\frac{6r}{6r+(3\Gamma_4+\Delta_4)P^2}\\
&+ \frac{1}{2}rP^2\left(1+\frac{K_{d+1}}{2}\left(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6}\right)\right)\\
&+ P^4\left(\frac{\Gamma_4+\Delta_4}{4!}-\frac{K_{d+1}}{8}\left(\frac{\Gamma_4}{2}+\frac{\Delta_4}{6}\right)^2\right). \qquad (21)
\end{aligned}$$

where Γ_4 and Δ_4 are P-dependent and are to be determined from the set of equations[11]. We notice that only the following combinations of Γ_4 and Δ_4 appear in all the calculations,

$$\begin{aligned}
\gamma_1 &= 3\Gamma_4+\Delta_4,\\
\gamma_2 &= \Gamma_4+\Delta_4. \qquad (22)
\end{aligned}$$

Here γ_2 is the coefficient for the quartic term in mean field approximation. On the other hand non-zero polarization enters into the fluctuation propagator with a coupling constant γ_1. In case of $\gamma_2<0$, a mean field picture requires an additional $|P|^6$ term with positive coefficient for the stability of the system. However a fluctuation corrected scenario can ensure stability without such a term, provided $\gamma_1>0$. With the above definitions, the set of equations[12] becomes a single self-consistent equation for γ_1

$$\begin{aligned}
\gamma_1 &= \frac{3\Gamma_4^0}{1+\frac{3}{2}K_{d+1}\Gamma_4^0x}\\
&\times \left(1+\frac{\Delta_4^0}{\Delta_4^0+(3\Gamma_4^0-\Delta_4^0)(1+\frac{3}{2}K_{d+1}\Gamma_4^0x)}\right) \qquad (23)
\end{aligned}$$

Here x contains γ_1 only. Solving the above equation, γ_2 can be found from (eqn. [11])

$$\frac{d\gamma_2}{dx}=-\frac{K_{d+1}}{6}\gamma_1^2. \qquad (24)$$

Below $\gamma_2=0$, phase transition in this system will be first order. We are interested in the phase transition near $\gamma_2=0$, where fluctuation effects in four point vertices are important. If we limit ourselves to the region $|\Delta_4|<3\Gamma_4$, the leading order behavior of γ_1 is same as that of Γ_4 and is given by

$$\begin{aligned}
\gamma_1 &\approx \frac{3\Gamma_4^0}{1+\frac{3}{2}K_{d+1}\Gamma_4^0x}\\
&= \frac{3\Gamma_4^0}{1+\frac{3}{2}K_{d+1}\Gamma_4^0\log\frac{6\Lambda}{\sqrt{6r+\gamma_1P^2}}}. \qquad (25)
\end{aligned}$$

Assuming the bare value $\Gamma_4^0\sim\mathcal{O}(10)$, so that $\frac{\Gamma_4^0}{4!}<1$ which validates perturbation theory, gives $6\Gamma_4^0\sim\mathcal{O}(10^2)$. If we define a parameter $a=\frac{3}{4}K_{d+1}\Gamma_4^0$, then within the validity regime of perturbation theory $a\sim\mathcal{O}(10^{-1})$. Thus for an wide range of γ_1 e. g. $\gamma_1\sim\mathcal{O}(1)-\mathcal{O}(10^2)$, we find $|a\log\gamma_1|<|\frac{3\Gamma_4^0}{\gamma_1}|$. For small r, γ_1 and γ_2 can be estimated as

$$\gamma_1\sim\frac{3\Gamma_4^0}{1-a\log(\gamma_1P^2)}\approx\frac{3\Gamma_4^0}{1-2a\log P} \qquad (26)$$

This is essentially a non-self-consistent solution for γ_1. Variation of γ_1 at zero temperature is shown in figure [2]. However from the equation [24], we get,

$$\begin{aligned}
\gamma_2 &= \gamma_2^0+(-9(\Gamma_4^0)^2+\frac{\gamma_1}{3})\\
&= \gamma_2^0-\frac{9(\Gamma_4^0)^2K_{d+1}}{6a}\left(1-\frac{1}{1-2a\log P}\right) \qquad (27)
\end{aligned}$$

where γ_2^0 is the bare value of γ_2. Since the corrections due to self-consistency $\sim \log\gamma_1$, the above estimate breaks down near $P \sim \exp(1/2a)$. Except in that regime, the non-self-consistent result is expected to give good result. *Free energy at* $T = 0$: Using the asymptotic behavior of the four point vertices[26] and using equation [21] with a redefinition of γ_2^0 as $\gamma_2^0 - \frac{9(\Gamma_4^0)^2 K_{d+1}}{6a}$, we can write the following asymptotic expression for the free energy at zero temperature

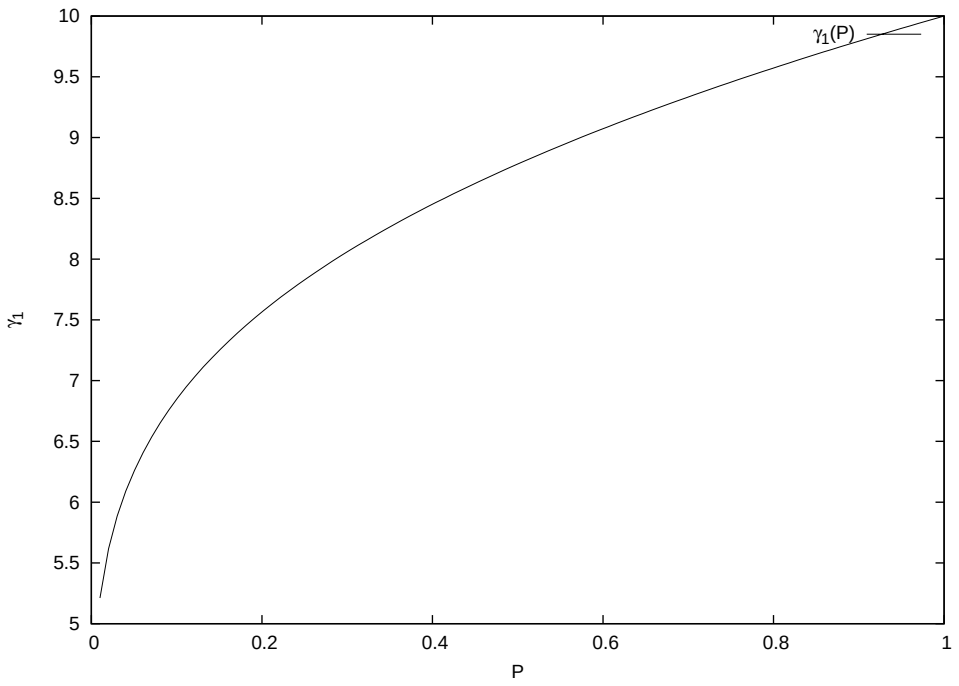

FIG. 2: Asymptotic evolutions of γ_1 with P at $T = 0$. Parameter values are $3\Gamma_4^0 = 10$ and $a = 0.1$.

$$
\begin{aligned}
F &= \frac{K_{d+1}}{4} r^2 \log \frac{6r}{6r + P^2 \frac{3\Gamma_4^0}{1-2a\log P}} \\
&+ \frac{1}{2} r P^2 \left(1 + \frac{K_{d+1}}{12} \frac{6\Gamma_4^0}{1 - 2a\log P}\right) \\
&+ \frac{P^4}{4!}(\left(\gamma_2^0 + \frac{K_{d+1}}{6a}\left(\frac{9(\Gamma_4^0)^2}{1 - 2a\log P}\right)\right) \\
&- \frac{4! K_{d+1}}{36 \times 8}\left(\frac{3\Gamma_4^0}{1 - 2a\log P}\right)^2). \qquad (28)
\end{aligned}
$$

Here the first term $\sim \mathcal{O}(r^2)$, hence small. The second term is a standard quadratic term with fluctuation corrections. The third term, describes the appropriate physics of the problem. The coefficient of the quartic term contains three terms. First one is a constant and can take either positive or negative but small values. Now there is a competition between the second and the third term. The second term tries to make the free energy positive while the third term tries to make it negative. However unless γ_2^0 is a sufficiently large negative number, coefficient of the quartic term is positive in the parameter regime of our interest.

Possibility of a first order transition: To have a phase transition, the following equation must be satisfied,

$$
\frac{\partial F}{\partial P} = rP + \frac{1}{3!}(\Gamma_4 + \Delta_4)P^3 = 0 \qquad (29)
$$

For positive $r \approx 0$, the above equation can be satisfied only if $\Gamma_4 + \Delta_4$ is negative. Corresponding value of the P is given as,

$$
P_0 = \exp\left(\frac{1}{2a} + \frac{9K_{d+1}(\Gamma_4^0)^2}{12a\gamma_2^0}\right) = \exp\frac{1}{2a}(1 + \mu) \quad (30)
$$

Where μ is defined as

$$
\mu = \frac{9K_{d+1}(\Gamma_4^0)^2}{6\gamma_2^0} \qquad (31)
$$

Since $|\mu| >> 1$, the parameter $\gamma_2^0 > 0$ corresponds to the very large values of P_0. Since the scheme presented here, is valid for small P, we exclude this possibility in this discussion. On the other hand, $\gamma_2^0 < 0$ corresponds to the finite value of P_0 and there is a possibility of a first order transition at $r = r_0 > 0$. As $r \sim P^2$, $r_0 \sim \exp\frac{1}{a}(1 + \mu)$. If we consider the Gaussian thermal fluctuations near the instability point and neglect the temperature dependencies of the vertices, then the thermal corrections to r and $P^2 \sim T^2$ and P_0^2 should vanish above a temperature $T \sim \exp\frac{1}{2a}(1 + \mu)$. However the parquet equations for the vertices and hence the form of fluctuation renormalized free energy should get changed at finite temperature. In the next section we will discuss the finite temperature case in detail.

IV. FLUCTUATION CORRECTIONS TO THE FREE ENERGY AT NON-ZERO TEMPERATURE



FIG. 3: Diagrammatic representation of gap renormalization up-to one loop.

Here we consider the system to be near the mean field quantum critical point with a zero temperature negative gap(i. e. $r = -r_0$, $r_0 \geq 0$). Near $r_0 = 0$, the zero temperature gap attains a finite temperature value $r(T)$ as follows.

$$
r(T) = -r_0 + K_d(\frac{u}{2} + \frac{v}{6})T^2 \qquad (32)
$$

Here the thermal fluctuations are considered up-to the Gaussian level, and the above expression for $r(T)$ without any correction to four point vertices predicts a second order transition with a transition temperature $T_c \sim \sqrt{r_0}$. Now we will look at the correction to the four point vertices. Using the same procedure as used for the zero temperature case, we now deduce the parquet equations for the four point vertices and hence the free energy at finite temperature. At $T \neq 0$, fluctuation corrections to the four point vertices takes the form

$$
\begin{aligned}
\delta u &\sim -u^2 T \int_0^\Lambda d^3q G^2(q,\ \omega_n = 0) \\
&\sim -u^2 K_3 \frac{T}{(r(T) + (u/2 + v/6)P^2)^{\frac{1}{2}}} \qquad (33)
\end{aligned}
$$

in three dimension. Near the critical point, $r(T) \sim r + K_d(u/2 + v/6)T^2$, so at finite temperature, we can define our parquet variable as

$$x = \frac{T}{(r + (u/2 + v/6)(P^2 + K_d T^2))^{\frac{1}{2}}}. \tag{34}$$

The finite temperature parquet variable is defined as

$$x = \frac{T}{(r + (u/2 + v/6)(P^2 + K_d T^2))^{\frac{1}{2}}} \tag{35}$$

In this case, fluctuation corrections to the free energy in terms of γ_1 and γ_2 (equation [18]) becomes,

$$\begin{aligned} I_{fluc} &= -\frac{1}{4!}\int_{\frac{T}{(r+\frac{\gamma_1}{6}K_dT^2)^{\frac{1}{2}}}}^{\frac{T}{(r+\frac{\gamma_1}{6}(P^2+K_dT^2))^{\frac{1}{2}}}} \left(\frac{T^2/x^2 - r}{\gamma_1/6} - K_dT^2\right)^2 \frac{d}{dx}\gamma_2(x)dx \\ &= \frac{1}{4}[T[(r + \frac{\gamma_1}{6}K_dT^2)^{\frac{3}{2}} - (r + \frac{\gamma_1}{6}(P^2 + K_dT^2))^{\frac{3}{2}}] \\ &+ r^2[(r + \frac{\gamma_1}{6}K_dT^2)^{-\frac{1}{2}} - (r + \frac{\gamma_1}{6}(P^2 + K_dT^2))^{-\frac{1}{2}}] \\ &+ T^4\gamma_2^2[(r + \frac{\gamma_1}{6}K_dT^2)^{-\frac{1}{2}} - (r + \frac{\gamma_1}{6}(P^2 + K_dT^2))^{-\frac{1}{2}}] \\ &- Tr[(r + \frac{\gamma_1}{6}K_dT^2)^{\frac{1}{2}} - (r + \frac{\gamma_1}{6}(P^2 + K_dT^2))^{\frac{1}{2}}] \\ &+ 2rT^2\gamma_2[(r + \frac{\gamma_1}{6}K_dT^2)^{-\frac{1}{2}} - (r + \frac{\gamma_1}{6}(P^2 + K_dT^2))^{-\frac{1}{2}}] \\ &+ T^4\gamma_2[(r + \frac{\gamma_1}{6}K_dT^2)^{-\frac{1}{2}} - (r + \frac{\gamma_1}{6}(P^2 + K_dT^2))^{-\frac{1}{2}}]] \end{aligned} \tag{36}$$

In performing the above integral x-dependence of Γ_4 and Δ_4 are neglected. For the systems near $r \to 0$ limit, retaining only the terms lowest order in T and r, the free energy can be truncated as

$$\begin{aligned} F &= \frac{1}{2}rP^2 + P^4(\frac{\Gamma_4 + \Delta_4}{4!}) \\ &+ \frac{T}{4}[(r + K_d(\frac{\Gamma_4}{2} + \frac{\Delta_4}{6})T^2)^{\frac{3}{2}} \\ &- (r + (\frac{\Gamma_4}{2} + \frac{\Delta_4}{6})(P^2 + K_dT^2))^{\frac{3}{2}}] \end{aligned} \tag{37}$$

For small r and T, the third term is of the $\mathcal{O}(T^4)$, hence is negligible. Thus the free energy in the leading order can be further truncated as

$$F = \frac{r}{2}P^2 + P^4(\frac{\Gamma_4 + \Delta_4}{4!}) - \frac{T}{4}(\frac{\Gamma_4}{2} + \frac{\Delta_4}{6})^{\frac{3}{2}}P^3 \tag{38}$$

Following the calculations similar to that of the zero temperature case, we get the following expression for the free energy at the finite temperature.

$$\begin{aligned} F &= \frac{1}{2}rP^2 + P^4(\frac{\Gamma_4 + \Delta_4}{4!}) \\ &- \frac{T}{4}(\frac{\Gamma_4}{2} + \frac{\Delta_4}{6})^{\frac{3}{2}}P^3. \end{aligned} \tag{39}$$

In the above equation $P \equiv |\vec{P}|$ and the cubic term which is a result of small P expansion, does not violate the symmetry of the problem. A finite temperature version of the equation [26], i.e. the asymptotic form of the self consistent equation for γ_1, one of the important combinations of the four point vertices reads,

$$\gamma_1 = \frac{6\Gamma_4^0}{1 - \frac{6aT}{(\gamma_1(P^2+K_dT^2))^{1/2}}}. \tag{40}$$

Non-zero solution of the above equation tells

$$\begin{aligned} \gamma_1 &= \frac{18a^2T^2 + K_d\Gamma_4^0T^2 + \Gamma_4^0P^2}{P^2 + K_dT^2} \\ &\pm \frac{6aT\sqrt{9a^2T^2 + \Gamma_4^0P^2 + \Gamma_4^0K_dT^2}}{P^2 + K_dT^2}. \end{aligned} \tag{41}$$

In deriving the equations at finite temperature we have limited ourselves in the low temperature region i.e. a^2T^4 is neglected compared to K_dT^2. Moreover γ_1 should decrease at nonzero P and should go towards it's bare value with increasing P. Hence the part is remaining,

$$\gamma_1 \approx \Gamma_4^0 - \frac{6a\sqrt{\Gamma_4^0}T}{\sqrt{P^2 + K_dT^2}}. \tag{42}$$

Asymptotic evolution of γ_1 with P for two different temperature is shown in figure [4]. From equation[27]

$$\gamma_2 = \gamma_2^0 + \left(\frac{2\Gamma_4^0}{3} + \frac{2a\sqrt{\Gamma_4^0}T}{\sqrt{P^2 + K_dT^2}}\right). \tag{43}$$

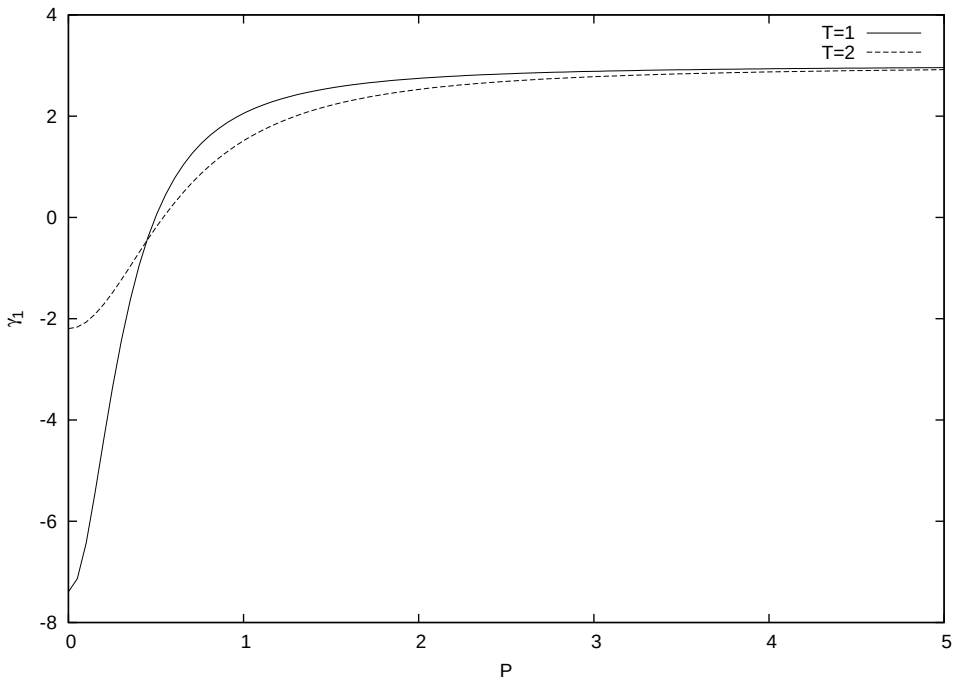

FIG. 4: Asymptotic evolution of γ_1 with P at $T \neq 0$. Two curves are drawn at two different temperatures with $\Gamma_4^0 = 10/3$, $a = 0.1$ and $K_d = 0.1$. Upper one is at $T = 1$ and the lower one is at $T = 2$ in some arbitrary scale.

Free energy at nonzero T: Again using the asymptotic behavior of the four point vertices[42] and using equation [39], we can write the following asymptotic expression for the free energy at non zero temperature

$$F = \frac{r(T)}{2}P^2 + \frac{P^4}{4!}\left(\gamma_2^0 + \left(\frac{2\Gamma_4^0}{3} + \frac{2a\sqrt{\Gamma_4^0}T}{\sqrt{P^2+K_dT^2}}\right)\right) - \frac{T}{4}P^3\left(\frac{\Gamma_4^0}{6} - \frac{a\sqrt{\Gamma_4^0}T}{\sqrt{P^2+K_dT^2}}\right)^{\frac{3}{2}}. \quad (44)$$

Gap renormalization up-to one loop(figure [3]) at finite temperature near $r = 0$, tells,

$$r(T) = -r_0 + K_d\left(\frac{\Gamma_4^0}{6} - \frac{a\sqrt{\Gamma_4^0}T}{\sqrt{P^2+K_dT^2}}\right)T^2. \quad (45)$$

Neglecting the term of $\mathcal{O}(T^{-3})$ in the coefficient of P^2, the expression for free energy becomes

$$F = \frac{1}{2}\left(-r_0 + \frac{K_d\Gamma_4^0}{6}T^2\right)P^2 + \frac{1}{4!}P^4\left(\gamma_2^0 + \left(\frac{2\Gamma_4^0}{3} + \frac{2a\sqrt{\Gamma_4^0}T}{\sqrt{P^2+K_dT^2}}\right)\right) - \Gamma_4^0\frac{T}{4}P^3\left(\frac{1}{6} - \frac{3aT}{2\sqrt{\Gamma_4^0(P^2+K_dT^2)}}\right). \quad (46)$$

In the limit $P^2 >> K_dT^2$, it takes the form

$$F = \frac{1}{2}(-r_0 + \frac{K_d\Gamma_4^0}{6}T^2 + \frac{3aT^2\sqrt{\Gamma_4^0}}{2})P^2 - \frac{T}{24}P^3(\Gamma_4^0 - \frac{a}{2}\sqrt{\Gamma_4^0}) + \frac{(\frac{2\Gamma_4^0}{3} + \gamma_2^0)}{4!}P^4. \quad (47)$$

Possibility of the first order transition: The above equation tells that, the solution of the equation $\partial F/\partial P = 0$ will result a nonzero value of $P_0 \sim T_0$, even if $\gamma_2^0 > 0$. Here T_0 is the second order transition temperature for the mean field theory. Since near QCP, $T_0 \sim \sqrt{r_0}$, P_0 is also $\sim \sqrt{r_0}$. If we compare this results with that of the zero temperature case, we see that in both cases first order transitions is certainly weak. But in the finite temperature case, the discontinuity in the order parameter near the transition point $\sim \sqrt{r_0}$ and since r_0 is the smallest scale(near mean field QCP, $r_0 \to 0$) in this system, first order transition as a result of the order parameter fluctuations at finite temperature near the mean field QCP is weaker than that of the zero temperature case. Possible reason of such a result will be discussed in the next section.

V. DISCUSSIONS

Occurrence of first order transition due to coupling between the order parameter and soft modes is a well studied problem in many classical systems[12],[13],[14],[15] and recently in quantum phase transitions in electronic systems[16]. To capture the basic physics near a weak first order transitions, one needs to study the effects of fluctuations on the proper four point vertices. Bare perturbation calculations in this system show vertex corrections to be logarithmically singular at zero temperature in three spatial dimensions. We use parquet re-summation to derive recursion relations for four point vertices. Here the renormalized vertices crucially depends on the non-zero polarization. Using these relations expressions for free energy suitable for describing transitions at zero temperature and at finite temperature are derived. The relevant quantities like transition temperature and the discontinuity in the order parameter at the transition point turn out to be small but finite. We mainly concentrate on the phenomena near a *quantum critical point* predicted by a mean field theory. We found stronger possibility of first order transitions at $T = 0$ than at any finite temperature transition near QCP which is in accord with recent experimental finding. It is found that a finite polarization tries to suppress fluctuations. In such a scenario, we found that exploiting the logarithmic singularity in the vertex corrections, the zero temperature system is able to gain a finite possibility to undergo a first order transition near mean field QCP while the finite temperature one fails to do so. Moreover unlike the standard RG approach, which considers first order transition as just the inability of the system to reach an unstable fixed point, the present approach makes qualitative predictions about the magnitude of the discontinuity in order-parameter near the transition point. Similar phenomena occurs in low T_c itinerant magnets because of the coupling between order parameter and other soft modes[17]. The effects of fluctuations in the discontinuity in order-parameter has been estimated earlier using loop corrections to the free energy, hence an non-analytic Landau expansion. In those works the occurrence of first order transition at low temperature is concluded to be generic. We look at the similar problem in a different physical system and emphasize the importance of competition between fluctuations and nonzero polarization and the crucial role played by marginal dimensionality. We have considered the constant pressure case only where strain effects are completely integrated out. One can also consider a situation where system volume is constant and a proper quantum generalization of such case[18] should certainly be addressed.

Acknowledgment

We are grateful to Prof. T. V. Ramakrishnan for his constant encouragement and for providing us with a copy of the unpublished PhD Thesis of Dr. S. N. Gadekar.

---

[*] Electronic address: nabyendu@iopb.res.in, mishra@iopb.res.in

[1] Muller K A and Burkard H, PRB 19, 3593 (1979).

[2] Das N and Mishra S G, J. Phys.: Cond. Mat 21, 095901 (2009).

[3] Palova, Chandra P and Coleman P, PRB 79, 075101 (2009).

[4] Roussev and Millis A J, PRB 67, 014105 (2003).

[5] Samara G, Phys. Rev. 151, 378-386, (1966).

[6] Taniguchi, Itoh, and Yagi, PRL 99, 017602 (2007).

[7] Lemanov, Smirnova, Syrnikov, and Tarakanov, PRB 54, 3151 (1996).

[8] Gadekar S N and Ramakrishnan T V, J Phys C: Solid St. Phys. 13, L957 (1980)

[9] Gadekar S N PhD Thesis(unpublished), Dept. of Physics, IIT, Kanpur (1977).

[10] Ginzburg S L, Sov. Phys. JETP 39, 312 (1974).

[11] Polyakov A M, JETP 30, 151 (1970).

[12] Larkin A I and Pikin S A, JETP 29, 891 (1969).

[13] Lyuksyutov I F and Pokrovskii V L, JETP Lett 21, 9 (1975).

[14] Rudnick J, PRB 18, 1406, (1978).

[15] Jacobson H H and Amit D J, Annals of Physics, 133, 57 (1981).

[16] D Belitz, T R Kirkpatric, T Vojta, Rev. Mod. Phys. 77, 579 (2005) and the references therein.

[17] D Belitz, T R Kirkpatric, T Vojta, Phys. Rev. Lett. 82, 4707 (1999)

[18] Bergman D J, Halperin B I, PRB 13, 2145 (1976).